



UNIVERSITÀ
DEGLI STUDI
DI UDINE

Università degli studi di Udine

Innovative bioaerogel-like materials from fresh-cut salad waste via
supercritical-CO₂-drying

Original

Availability:

This version is available <http://hdl.handle.net/11390/1138471> since 2020-02-27T15:29:45Z

Publisher:

Published

DOI:10.1016/j.ifset.2018.04.022

Terms of use:

The institutional repository of the University of Udine (<http://air.uniud.it>) is provided by ARIC services. The aim is to enable open access to all the world.

Publisher copyright

(Article begins on next page)

Manuscript Details

Manuscript number	IFSET_2017_1193_R1
Title	Innovative bioaerogel-like materials from fresh-cut salad waste via supercritical-CO ₂ -drying
Article type	Research Paper

Abstract

Fresh-cut salad waste was dried by means of supercritical carbon dioxide technology using ethanol as co-solvent. The obtained material was characterized by a white color and a brittle texture. Microscopic images revealed an aerated structure, with well-evident intra and inter-cellular spaces. Based on the high internal surface (>100 m²/g), the extremely low density (<0.5 g/cm³) and the high porosity (>80%), supercritical-dried salad waste can be regarded as a bioaerogel-like material. One gram of this material absorbed 33 and 19 g of water and oil respectively. Industrial application: Fresh-cut processing of salad generates large amounts of solid waste which is not suitable for conversion into biogas or fertilizers. This waste poses management issues for producers and represents an environmental burden. Fresh-cut salad waste could be valorized to produce bioaerogel-like materials with enhanced solvent uptake ability, to be exploited as food ingredients, packaging, absorbents or innovative carriers for both lipophilic and hydrophilic compounds.

Keywords	supercritical drying, salad waste, waste valorization, aerogel, porosity
Corresponding Author	Sonia Calligaris
Corresponding Author's Institution	University of Udine
Order of Authors	Stella Plazzotta, Sonia Calligaris, Lara Manzocco

Submission Files Included in this PDF

File Name [File Type]

Cover Letter.docx [Cover Letter]

Answers to the editors and reviewers.docx [Response to Reviewers]

Highlights.docx [Highlights]

Manuscript_2nd subm.docx [Manuscript File]

Figures.docx [Figure]

Supplementary data.docx [Figure]

To view all the submission files, including those not included in the PDF, click on the manuscript title on your EVISE Homepage, then click 'Download zip file'.

Dear Editor,

We send to your attention the research article "**Innovative bioaerogel-like materials from fresh-cut salad waste via supercritical-CO₂-drying**" by Stella Plazzotta, Sonia Calligaris and Lara Manzocco, revised according to the reviewers' suggestions and corrections.

Best regards,

Sonia Calligaris

Answers to the editors and reviewers:

Reviewer 1

This paper reports supercritical drying of salad waste and its absorption properties. I recommend the paper for publication after the following points are clarified:

1. On page 11, line 256, the authors pointed out that the high specific surface area of the aerogel compared to those of air dried samples is attributed to cell swallowing, or expansion, during drying. I don't think this speculation is correct because, i) In general, supercritically dried samples fundamentally show high specific surface areas compared to ambient dried samples because of the absence of surface tension during the drying process. ii) Simple expansion increases the volume of the sample, but it would not greatly affect internal surface areas. iii) You cannot simply compare the unit weights of air dried and supercritically dried samples. Supercritical drying also eliminates some CO₂-soluble solids from the samples, e.g., pigments (page 10, line 235). See also comment 2 below.

i) We agree with the reviewer's observations that supercritical drying usually prevents sample collapse rather than promoting its expansions. This observation was added in the text (lines 309-313).

ii) Thank you for the observation. Mention to increase in sample area were omitted.

iii) The role of ethanol/CO₂ soluble compounds was discussed (lines 262-267, 318-321, 394-398).

2. On Page 13, line 314, the authors pointed out that the aerogel sample absorbs much water than fresh salad tissue because fresh salad contains 16 g water/1 g dry sample, while the aerogel absorbs ~35 g water/1 g dry sample. This item should be discussed more carefully. The fresh salad also contains some compounds that are removed via extraction with ethanol and/or supercritical CO₂. The author should provide the chemical composition of the fresh salad: the ratio of water, CO₂-insoluble components, and CO₂-soluble components.

Discussion was improved by considering that removal of ethanol and CO₂ soluble compounds could favor exposure of hydrophilic groups and thus contribute to the development of a material able to uptake high amounts of water (lines 394-398). Composition of salad waste was added (lines 99-104, 258-267, Table 1) and the loss of compounds during the treatment, due to their solubility in both ethanol and CO₂ was discussed (lines 262-267, 318-321, 394-398).

3. The authors also pointed out that the CO₂-dried sample has hydrophilic surface. In the case of silica aerogels, this is reasonable because supercritical-CO₂-dried silica has strongly hydrophilic

surface due to the formation of Si-OH surface groups during the drying. In the present study, the authors should provide the experimental evidence for hydrophilicity and its origin, e.g., FT-IR, contact angle measurements.

The hygroscopicity and hydrophilicity of the material were evaluated (lines 181-198) and shown in two new supplementary figures (Supplementary Figure C and D). Additional considerations about material hydrophilicity were added in the text (lines 396-398).

4. The manuscript is well-organized and easy to follow. But, in my opinion, the authors should provide some raw data for the physicochemical properties described in Tables 1 and 2, e.g., stress-strain curves, DSC profiles, nitrogen isotherms, fitting curves, at least in the Supporting Information. Two supplementary figures relevant to material hygroscopicity and hydrophilicity were added in the supplementary data (Supplementary Figure C and D). Fitting was performed in a single step for the material isotherm and for oil and water absorption kinetics. Fitting curves were thus reported in Figure 2 and 3 and data in Table 4 were amended accordingly. In addition, stress-strain curves, nitrogen isotherms and a figure showing the appearance of the material after water imbibition were selected to be inserted in the paper supporting information (Supplementary Figure A and B).

5. The horizontal axis label in Figure 2 is not displayed properly.

The error was corrected.

Reviewer 2

This manuscript presents an innovative idea of using salad waste to produce aerogels. The subject is clearly worthy of investigation, the applied characterization methods are appropriate, and the manuscript is generally well written. I suggest to consider the following points before the publication of this manuscript:

1) There seems to be a conflict between the BET surface area and pore size determination by optical microscopy, as those two methods may detect structures of different size ranges. The reported surface area would suggest a smaller pore size than that observed by microscopy. Were there pores in the mesoporous range that were not visualized by microscopy? Was the average pore size analyzed from the BET sorption results?

The discussion about porosity was modified, taking into account the reviewer's considerations. Actually BET and microscopy were able to detect different structures, that were distinctly discussed (lines 199-225, 300-307, 316-325, Table 3).

2) Please discuss the possibilities of manufacturing monoliths of various dimensions of the salad waste. Are the macroscopic dimensions of aerogels determined by the original dimensions of the salad leaves? How easy was it to cut the samples for e.g. mechanical testing and to obtain smooth surfaces?

This topic was discussed in the conclusions section (lines 429-432). Our material resulted brittle (according to stress-strain curves) but not difficult to cut.

3) Please report the possible shrinkage of the material upon ethanol treatment and drying

This topic was discussed in the text (lines 283-286).

4) Please discuss potential drawbacks of salad waste as raw material. The outer leaves remaining in the waste stream may be bruised and / or microbiologically spoiled. How does this affect the aerogel preparation and potential applications?

This topic was discussed in the conclusions section (lines 422-428).

Reviewer 3

General:

The supercritical drying of cellular structures without necessary pretreatment (e.g. gel formation) is worth of investigation. Costly production steps of gel formation are not necessary and make it attractive. However, the technology is not new (Brown et al., 2007), but the performed analytics reveal new insights into the characteristics of such materials. Authors present the results of only one kind of sample (supercritically dried salad leaves) with one drying setup configuration. Hence the results of a single sample are presented. This leaves no possibility for comparison. The discussion of the present results is very short and a comparison to other materials presented in literature only takes place to a very limited extend.

We agree with the reviewer that the CO₂ drying is not new and has been proposed as alternative to freeze-drying to obtain high quality dried vegetable foods (see Brown et al., 2008). In our paper, we propose its exploitation to obtain food-grade materials which could be used to other purposes (e.g. moisture absorbents, templates for oleogels, biodegradable packaging). For this reason, the obtained material was characterized for physical and physico-chemical properties rather than for those properties which are usually assessed to evaluate dried food quality. This innovative approach

provided new insights in the material properties but reduces the possibility of comparison with literature results.

We decided to focus on salad waste, being representative of a number of plant waste materials, which are generally associated with management issues. As stated in the conclusions, it is likely that other waste materials could be similarly exploited.

Authors claim as industrial relevance that a valorization of the material is possible, but the technology is very expensive. Does the added value justify the process?

We agree with the reviewer about the high cost of the supercritical-drying technology. It can be hypothesized that turning a vegetable waste into a bio-aerogel like material with high loading solvent capacity would allow to reduce waste management issues as well as give a market value to the derived material. This topic was discussed in the conclusions section (lines 422-428). To assess the actual feasibility of this technology to salad waste, the evaluation of sustainability, economic and consumer impact of the obtained material should be investigated. Life Cycle Analysis could be exploited to this aim, which was however out of the scope of the present paper.

The discussion needs to be extended towards a clear hypothesis and description of how the existent structure, which is the obvious advantage of the material, will be transferred into an actual packaging, insulating or transportation material. Bioaerogels are gelled in the desired geometrical dimensions prior to supercritical drying. How is this intended with the described material?

Specific approaches should be adopted to provide the bioaerogel-like material with the desired shape, making it independent on the original dimension of the used vegetable waste. To this regard, the application to the ground vegetable waste of approaches commonly used to produce hydrogel and oleogel templates could be evaluated. More comments were added in the conclusion section (lines 428-432).

Providing that the authors have a clear prospect of how this is accomplished and they intensify the discussion, I recommend the manuscript for publication after major revision, since I clearly see the innovation and possible advantages of the subject.

Critical points in detail are:

The article needs revision on spelling and wording. Examples are given in the following list.

Line 126: Spelling Heerbrg

The mistake was corrected (lines 139-141).

Line 201, 232, 232, 261: Space missing

Text was carefully controlled.

Line 55: 'beget' is mainly used in a different context (beget a child).

The term was changed in "produce" (line 50).

Line 51: It is not clear whether the word 'process' refers to the solvent exchange or to the supercritical drying process.

The term was changed in "supercritical-CO₂-drying" (line 46).

Line 271: 'controlled release in pharmaceuticals'

The mistake was corrected (line 332).

Line 103-105: The sentence is not clear. Reword. What is meant by visually assessed? This is very subjective.

The sentence was reworded (lines 95-96).

Line 137: Second sentence, wording.

The mistake was corrected (line 143).

Line 241, 251, 258: Wording. Do the authors mean swelling instead of swallowing? Reword 'peculiar swallowed'. Peculiar is more in the sense of unexplainable, which it is not, and swallowed is unclear. What is meant by 'cell swallowing'.

The term was changed into "swelling" (lines 279-281).

Line 330-332: Reword the sentence. It is hard to read.

The sentence was reworded (lines 411-412)

Materials and Methods is in many cases not precise enough. Clarification is necessary in the following examples:

Line 82: Point out more clearly that it is the outer leaves which are considered as salad waste and are the actual subject of investigation.

The fact that outer leaves are considered as salad waste was better specified (lines 77-78).

Line 84: Is the mass of the outer leaves of relevance for the investigated subject and where does a standard deviation come from? Was this registered per salad head? How is 'outer leaves' defined?

Amount data was removed. As better explained in lines 76-78, salad heads were treated simulating industrial fresh-cut operations and thus outer leaves are those commonly removed during such operations.

Line 85: Is the washing in a chlorinated bath with NaClO a standard process in the production process? Is it afterwards still applicable in food products? Authors promote the application in food products.

The washing in chlorinated water at 200 mg/L is a standard operation for fresh-cut products and thus the obtained material could still be used in food products.

Line 93: What was the final ethanol concentration in the surrounding solution? This has a major effect on the drying process. This question applies also to Line 98.

The concentration of the last ethanol solution was 99.04%, which, considering the alcoholmeter error, falls within the magnitude range of absolute ethanol concentration. For this reason, a complete substitution of compositional water by ethanol was assumed. Sentence was reworded (86-87).

Line 101: Explain the process in more detail. 5 g of sample, is this a stack of 5 cm x 5 cm pieces? Is it one piece?

Sample dimensions were reported more in detail (lines 82, 93, 202).

Line 107: Was a modification during storage monitored? P2O5 may initiate noteworthy drying of residual water, especially when water was not fully replaced by ethanol.

No change in sample weight was detected during storage up to 90 days.

Line 130: What about the BJH-method? This should deliver much more accurate results.

Both BET and microscopy were taken into consideration to discuss porous structure at different levels of size magnitude (lines 200-225, 300-307, 316-325).

Line 153: Were 5 mg of sample ground or cut?

Required information was added in line 158.

Line 165, 174, 188: Samples were described as very brittle. How was it possible to cut them in 2 x 2 cm squares? Where do differently sized samples come from. Original samples were cut in 5x5 cm. Outline more clearly the sample preparation and sample appearance.

Dimension units were harmonized and sample dimensions were reported more in detail in the different sections of material and methods (lines 82, 93, 202). Brittle materials break under a tensile stress without significant deformation (e.g a sheet of paper). This doesn't necessarily mean they are difficult to cut. Our material resulted brittle (according to stress-strain curves) but not difficult to cut.

Line 182: What was the cutting method used to obtain particles?

Required information was added in line 211.

Line 183: The drying temperature is very high. Did any changes occur on the sample? Was a further weight loss monitored (residual water)?

Required information was added in line 212-213. Such pre-treatments are reported in the literature for other vegetable matrices (Amin et al., 2015).

Line 190: Outline more clearly the function of the plastic filter.

Required information was added in line 229-230.

Line 213: How was it guaranteed that all pores were filled with oil? What about helium pycnometry?

As regards oil imbibition, we referred to a methodology previously reported in the literature by Khosravi & Azizian (2016). This methodology is based on the fact that, in a porous structure, small size pores are occupied by oil before the bigger ones. In the light of this interpretation, it can be inferred that pore size should not be a limiting factor for complete filling of the porous structure. Text was improved accordingly to these considerations (lines 301-302).

Line 219: Authors talk about ‘two measurements’. Two equivalent measurements of the same sample should always deliver the same results. There is no added value. Furthermore, many methods may only be carried out once on one sample (Texture analyzer, DSC). Be more specific about how many experiments were carried out to attain reproducible results.

Two analytical repetition were performed on two replicated samples. Sentence was modified to increase clarity (lines 248-249).

Technology:

Line 250: How was cutting of this brittle material possible for further analytics?

Tense tests revealed that the material was brittle. Nevertheless, it could be easily cut by simply using a sharp blade.

Line 262: Why is subsequent water removal necessary after supercritical drying? The process should be adjusted to producing samples without residual water.

Sentence was modified, as it was confounding and not clear. No residual water was present in the sample (lines 320-321).

Line 283: Figure 2: How was a_w 0 and 100 accomplished? In Materials and Methods 11 and 96% are described as highest and lowest values for relative humidity.

Materials and methods were modified, adding information about 5 and 100% ERH (0.05-1 a_w) (lines 144-146). Figure 2 was modified accordingly.

Line 288: Authors claim that the samples did not lose their integrity. Were they still brittle and appeared dry or more like a wetted cloth?

The material appeared like a wetted cloth (lines 405-406). A clarifying image, showing sample appearance, was added in the supporting material (Supplementary Figure E).

Discussion:

Line 234: (Figure 1) The L, a, b values do not supply valuable information to the reader, especially as the color change is obvious in the photographs. What meaningful information do the authors gain from the values?

It is our impression the complete loss of green color of the material is worthy mention. It accounts for porosity increase and removal of pigments. In addition, a white material could have larger possibilities of exploitation in several sectors.

Line 248: Specific heat is described as low, but compared to what? Discuss in more detail.

Sentence was rephrased, to underline that specific heat is simply comparable to that of similar dried vegetable matrices (lines 289).

Line 73: The poor composition of salad waste is mentioned. Why is it poor and what makes it then suitable for bioaerogel like materials? The composition is the same as in salad.

Table 1 was added, showing salad waste composition. Salad waste is actually not profitable for most recovery strategies as it is mainly represented by water and has low contents of bioactives as compared to other vegetable wastes. Text was improved (lines 66-68). Conversion to bioaerogel could allow exploitation of the salad structural architecture to obtain brand new materials.

Line 76: It would be helpful to outline the reasons for performing the analytics. What can be extracted and what is the new value.

Text was improved accordingly to the reviewer's suggestion (lines 70-72).

Line 253: Why is the brittle texture a reason for direct use in food systems. Discuss in more detail.

Most aerogels are very hard materials, difficult to cut and impossible to eat. The salad aerogel is brittle but not hard to cut or chew. This explanation was added in the text (lines 292-294).

Line 257: Is the advantage of CO₂-drying not much more the retention of structure integrity but the ability to promote 'cell swallowing'?

We agree with the reviewer's comment and the sentence was thus modified (lines 309-313).

Line 267: The pore dimension is not discussed and is well above the typical pore dimension of aerogel materials, especially as it is out of the range of pores measurable using the BET method. The pores and therefore the surface measured using BET are mesopores and therefore in the range of 2 - 50 nm.

The discussion about porosity was modified. Both BET and microscopy were taken into consideration to discuss porous structure at different levels of size magnitude (lines 300-307, 316-325, Table 3).

Line 323: Mind the difference between loading efficiency and loading capacity. Ahmadi et al. (2016) had only about 2.5 % oil in their aerogels. They had a loading efficiency (% initially added to loaded on capsules) of 70 %.

The text was corrected (line 405).

Line 324: The oil holding capacity would be an interesting parameter. Is the oil kept inside or can the structure be described as a saturated sponge? The amount of oil makes it hard to imagine as dry brittle pellet with absorbed oil but rather a wet cloth containing large amounts of oil. In the latter case, the material would eventually be suitable as moisture absorbent but probably not as carrier system. Discuss in more detail.

Thank you for the advice. Text was improved accordingly (line 406-408).

Line 337: Low firmness and brittleness do not really qualify the material for further production steps as for example storage or transportation. Is it really possible to further process the dried material? Discuss in more detail.

Proper storage and packaging techniques should be defined once the commercial value of the material is proven. If this was true, packaging and transport solutions similar to those adopted for other brittle materials (dried pasta, eggs, bulbs, ...) could be adopted. Conclusion section was improved, by adding considerations about the possible issues related to the conversion of vegetable wastes into bioaerogel-like materials by supercritical drying (lines 422-432).

- 1 Porous materials can be obtained by supercritical-drying of vegetable wastes
- 2 Supercritical-CO₂-dried salad waste can be regarded as a bioaerogel-like material
- 3 Mechanical properties of dried salad waste would allow its use in food systems
- 4 Dried salad waste presented extremely high solvent loading capacity
- 5 Bioaerogel-like materials could be exploited as adsorbents and carriers

1 **Innovative bioaerogel-like materials from fresh-cut salad waste**
2 **via supercritical-CO₂-drying**

3 Plazzotta, S., Calligaris, S.*, Manzocco, L.

4 Department of Agricultural, Food, Environmental and Animal Sciences, University of Udine,
5 Italy

6 *e-mail: sonia.calligaris@uniud.it; Tel: +39 0432-558571

7 **Abstract**

8 Fresh-cut salad waste was dried by means of supercritical carbon dioxide technology using
9 ethanol as co-solvent. The obtained material was characterized by a white color and a brittle
10 texture. Microscopic images revealed an aerated structure, with well-evident intra and inter-
11 cellular spaces. Based on the high internal surface ($>100 \text{ m}^2/\text{g}$), the extremely low density (<0.5
12 g/cm^3) and the high porosity ($>80\%$), supercritical-dried salad waste can be regarded as a
13 bioaerogel-like material. One gram of this material absorbed 33 and 19 g of water and oil
14 respectively.

15 *Industrial application:* Fresh-cut processing of salad generates large amounts of solid waste
16 which is not suitable for conversion into biogas or fertilizers. This waste poses management
17 issues for producers and represents an environmental burden. Fresh-cut salad waste could be
18 valorized to produce bioaerogel-like materials with enhanced solvent uptake ability, to be
19 exploited as food ingredients, packaging, absorbents or innovative carriers for both lipophilic
20 and hydrophilic compounds.

21 **Keywords:** supercritical drying, salad waste, waste valorization, aerogel, porosity

22 **1 Introduction**

23 Aerogels are defined as microporous materials entrapping a gas phase within the pores (Jones,
24 2007). The term is generic and refers to a wide variety of materials, presenting low density
25 ($0.0003\text{-}0.5 \text{ g}/\text{cm}^3$), high surface area ($50\text{-}1200 \text{ m}^2/\text{g}$) and high porosity ($70.0\text{-}99.8\%$) (Fricke
26 & Tillotson, 1997). Based on their composition, aerogels can be classified into inorganic,

organic, hybrid and bioaerogels. Although studies about bioaerogels are still pioneering, they have raised great interest in the last years, being produced from natural sources such as cellulose and its derivatives, marine polysaccharides, starch and proteins (Stergar & Maver, 2016). Bioaerogels are biocompatible, biodegradable and food-grade, making them potentially applicable in medical engineering, sustainable packaging production and novel food development (Maleki, 2016). To this regard, bioaerogels were proposed as carriers for different solvents, due to their ability to absorb large amounts of liquids by capillary forces (Ahmadi, Madadlou, & Saboury, 2016; Comin, Temelli, & Saldaña, 2012; Ivanovic, Milovanovic, & Zizovic, 2016). In this context, they have been suggested as food bulking agents, templates for liquid oil structuring and innovative carriers of nano-sized biochemicals (Ahmadi et al., 2016; Manzocco et al., 2017; Ubeyitogullari & Ciftci, 2017).

To obtain bioaerogels, a two-step procedure is traditionally applied. Initially, hydrogels are produced by gelation of a biopolymer in an aqueous media. Following, hydrogel solvent is slowly removed by a flow of continuous supercritical-CO₂. The latter is commonly applied since it avoids the formation of liquid-vapor interfaces and capillary tensions, thus reducing local collapse and maintaining the original hydrogel network (Maleki, 2016). The time required for supercritical-CO₂-drying is generally reduced by an ethanol-assisted procedure. In this case, before drying, hydrogel aqueous phase is substituted with ethanol, which has a higher affinity to supercritical-CO₂ (García-González, Camino-Rey, Alnaief, Zetzl, & Smirnova, 2012; Viganó, Machado, & Martínez, 2015). **Supercritical-CO₂-drying** is regarded as sustainable since it is performed at mild pressure (<10 MPa) and temperature (<45 °C), often using recycled carbon dioxide (Ghafar et al., 2017).

It can be inferred that supercritical-CO₂-drying of biological systems other than biopolymer gels could also **produce** highly aerated structure, similar to that of bio-aerogels. For instance, moisture-rich plant tissues could represent optimal candidates for the preparation of bioaerogel-like materials. These vegetable matrices can be regarded as complex polymeric networks,

mainly structured by cell wall cellulosic fibers, embedding water within intra- and inter-cellular spaces. Water removal, while maintaining cellular organization, could possibly result in an aerated fibrous network with high internal surface area and porosity. Circumstantial evidence supporting this hypothesis could be the enhanced rehydration ability of fruit and vegetables submitted to supercritical-CO₂-drying (Brown, Fryer, Norton, Bakalis, & Bridson, 2008). The preparation of bioaerogel-like materials from vegetable tissues could present the advantage of simplifying the conventional production process, since not requiring the gelling phase. In addition, if applied to vegetable wastes, this technological strategy could allow valorization of industrial discards, which typically represent an environmental and economic burden (Raak, Symmank, Zahn, Aschemann-Witzel, & Rohm, 2017). Based on these considerations, the aim of the present study was to evaluate the possibility to exploit salad waste to produce bioaerogel-like materials by means of supercritical-CO₂-drying. Fresh-cut salad was chosen as an example of a vegetable waste with high water content, which is not profitable for conventional valorization strategies (e.g. biogas production, composting or bioactive extraction) due to its poor composition, that is mainly represented by water (>94% w/w) (Plazzotta, Manzocco, & Nicoli, 2017). Salad waste was submitted to ethanol solvent exchange and supercritical-CO₂-drying. Samples were then analyzed for optical, thermal, mechanical and structural properties as well as for the ability to uptake water and oil. Analyses were performed in order to get an insight in the physical and physico-chemical properties of the material to suggest possible applications.

2 Materials and methods

2.1 Vegetable material

A 10-kg batch of Iceberg salad (*Lactuca sativa* var. *capitata*) was purchased at the local market and stored overnight at 4 °C. Salad head were treated simulating operations that are industrially carried out during fresh-cut salad processing. In particular, outer leaves were removed and used for the experimentation. Leaves were washed with flowing water (18±1 °C) and sanitized 20

min in a chlorinated bath containing 200 mg/L of NaClO with a 100 g/L leaves/water ratio. Leaves were then rinsed with flowing water and centrifuged in a manual kitchen centrifuge (mod. ACX01, Moulinex, France) for 1 min. Salad waste was manually chopped in homogeneous pieces (about 2.5×5 cm) with a sharp knife and immediately submitted to solvent exchange.

2.2 Solvent exchange using ethanol

Salad waste was immersed (100 g/L) in pure ethanol (J.T. Baker, Centre Valley, USA) for 24 h twice. During this procedure, water was progressively and completely removed from salad leaves, as indicated by monitoring the alcoholic degree of the ethanol solution by a lab alcoholmeter (Alcolyzer plus, Anton Paar, Graz, Austria).

2.3 Supercritical- CO_2 -drying

Salad waste in which water had been substituted by ethanol was dried using a supercritical- CO_2 -drying plant developed at the Department of Agricultural, Food, Environmental and Animal Sciences of the University of Udine and previously described by Manzocco et al. (2017). Briefly, a salad piece of 2.5×5.0 cm was placed inside the 265 mL-volume stainless steel cylindrical reactor which was then pressurized with CO_2 at 11 ± 1 MPa and 45°C . The outlet flow through the reactor was set at 6.0 L/min. This flow value was selected since it allowed drying time to be minimized. Samples were considered dried when ethanol was no more detectable in the gaseous outlet. Decompression from 11 MPa to atmospheric pressure was then carried out in 30 min. Samples were stored in P_2O_5 at room temperature until use.

2.4 Salad waste composition

Moisture, ash, protein and fat content was calculated according to AOAC methods (AOAC, 1997). Total dietary fibre (TDF) was calculated according to the AOAC international method (AOAC, 1997) using a total dietary fibre assay kit (TDF – 100A, Sigma-Aldrich, St. Louis, Missouri, USA). Carbohydrates were calculated by difference from moisture, ash, fat, protein and TDF.

2.4.1 *Total polyphenolic content*

An amount 10 g of salad waste, trimmed with a sharp knife were extracted by reflux with boiling water for 60 min applying a dilution of 1:4 (w/v). Extracts were cooled at room temperature, vacuum filtered thorough Whatman no. 1 filter paper (Maidstone, UK), freeze-dried at -50 °C and stored in a desiccator containing P₂O₅ at room temperature until use. Total polyphenolic content (TPC) was determined using Folin-Ciocalteu reagent (Singleton & Rossi, 1985). The reaction mixture contained 100 µL of salad waste extract solubilised in water (1:10 w/v), 500 µL of the Folin-Ciocalteu reagent, 4 mL of water and 2 mL of a sodium carbonate-water solution (0.15 g/mL). After 2 h reaction at ambient temperature, mixture absorbance was read at 750 nm using US-Vis spectrophotometer (Shimadzu UV-2501PC, UV-Vis recording spectrophotometer, Shimadzu Corporation, Kyoto, Japan). A calibration curve was made with standard solutions of gallic acid in the range 0.1–1000 mg/L ($R^2=0.99$). Results were expressed as mg of gallic acid equivalents per g of dry weight.

2.4.2 *Chlorophyll content*

Salad waste was homogenized with ethanol (95% w/w) applying a dilution of 1:4 (w/v) and filtered. The chlorophyll content was determined spectrophotometrically (Shimadzu UV-2501PC, UV-Vis recording spectrophotometer, Shimadzu Corporation, Kyoto, Japan), using the Lambert-Beer law and the specific absorbance coefficient (α) for chlorophyll α in 95% ethanol ($84.6 \text{ L g}^{-1} \text{ cm}^{-1}$) (Lichtenthaler & Buschmann, 2001; Perucka, Olszówka, & Chilczuk, 2014). Results were expressed as µg of chlorophyll per mg of dry weight.

2.5 *Color*

Color determination was carried out on salad waste using a tristimulus colorimeter (Chromameter-2 Reflectance, Minolta, Osaka, Japan) equipped with a CR-300 measuring head. The instrument was standardized against a white tile before measurements. Color was expressed in L*, a* and b* Hunter scale parameters (Chen, Zhu, Zhang, Niu, & Du, 2010).

2.6 *Image acquisition*

Images were acquired using an image acquisition cabinet (Immagini & Computer, Bareggio, Italy) equipped with a digital camera (EOS 550D, Canon, Milano, Italy). The digital camera was placed on an adjustable stand positioned 45 cm above a black cardboard base where the samples were placed. Light was provided by 4 100 W frosted photographic floodlights, in a position allowing minimum shadow and glare. Images were saved in *jpeg* format resulting in 3456 x 2304 pixels.

2.7 Optical microscopy

Samples were observed at room temperature using a Leica DM 2000 optical microscope (Leica Microsystems, Heerbrugg, Switzerland). The images were taken at 200X magnification using a Leica EC3 digital camera (Leica Microsystems, Heerbrugg, Switzerland) and elaborated with the Leica Suite Las EZ software (Leica Microsystems, Heerbrugg, Switzerland).

2.8 Sorption isotherm

Samples were weighted and transferred into dried weighting bottles. The latter were then transferred into desiccators containing P₂O₅ and LiCl, CH₃COOK, CaCl₂, K₂CO₃, NaCl, KCl, K₂SO₄ saturated solutions and water with equilibrium relative humidity (ERH%) values of 5, 11, 25, 31, 43, 75, 86, 96 and 100%, respectively. Samples were kept inside desiccators until constant weight was reached. The Brunauer-Emmet-Teller (BET) sorption isotherm model (eq. 1) was fitted into water sorption data (Braunauer, Emmett, & Teller, 1938).

$$\frac{a_w}{m(1-a_w)} = \frac{1}{m_0 c} + \frac{c-1}{m_0 c} a_w \quad (1)$$

where a_w is the water activity, m is the moisture of the sample expressed as ratio between the weight (g) of absorbed water and the weight (g) of dry matter, m_0 is the moisture of the water monolayer, and c is an experimental constant.

2.9 Differential Scanning Calorimetry (DSC)

DSC analysis was carried out using a TA4000 differential scanning calorimeter (Mettler-Toledo, Greifensee, Swiss) connected to a Graph Ware software TAT72.2/5 (Mettler-Toledo).

Heat flow calibration was achieved using indium (heat of fusion 28.45 J/g). Temperature calibration was carried out using hexane (m.p. -93.5 °C), water (m.p. 0.0 °C) and indium (m.p. 156.6 °C). Samples were prepared by carefully weighing around 5 mg of cut sample in 160 µL aluminum DSC pans, closed with hermetic sealing. An empty pan was used as a reference in the DSC cell.

For determination of specific heat capacity (C_p , Jg⁻¹K⁻¹), dried salad waste was heated from 15 to 150 °C, at a constant heating rate of 10 °C/min and without purge gas. A blank curve was also recorded by submitting an empty sealed pan to the same analysis. C_p (40 °C) was determined according to the following eq. (2):

$$C_p = \frac{H}{r_T} \cdot \frac{1}{m} \quad (2)$$

Where H is the heat flow in mW, calculated as signal difference between sample and blank curve, r_T is the sample heating rate (K/s) and m is the sample mass in mg.

2.10 Specific volume and apparent density

Samples were cut into 2 × 2 cm square shape and accurately weighted. Sample volume was then measured by a CD-15APXR digital caliber (Absolute AOS Digimatic, Mitutoyo Corporation, Kanagawa, Japan) and expressed as specific volume (cm³/g). Sample apparent density (g/cm³) was then calculated as the ratio between sample weight and specific volume.

2.11 Mechanical properties

Sample mechanical properties were measured by uniaxial tensile test using an Instron 4301 (Instron LTD., High Wycombe, UK). The instrumental settings and operations were accomplished using the software Automated Materials Testing System (version 5, Series IX, Instron LTD., High Wycombe, UK). Rectangular samples (2 × 4 cm) were positioned between two clamps mounted on a 100 N tensile head at a 5 mm/min crosshead speed, with a gauge length of 1 cm. Stress-strain curves were obtained from the tensile tests. Tensile strength at break (N) and the elongation at break (mm) were used to characterize sample tensile strength.

2.12 Hygroscopicity

The hygroscopicity was determined by measuring the moisture absorption capacity of samples at a set relative humidity (RH) of 86% at 30 °C. For this purpose, saturated solution of potassium chloride (KCl) was used. Samples were kept in desiccators with the set RH and weighed over time until a constant weight was reached. The percentage of moisture sorption (MS) was calculated from eq. (3):

$$MS = \frac{W - W_0}{W_0} \times 100 \quad \text{eq. (3)}$$

where, W (g), and W_0 (g) are the material weight after moisture sorption and its initial weight, respectively (Su et al., 2010).

2.13 FTIR measurement

Spectra were recorded at 25 ± 1 °C using a FTIR instrument, equipped with a ATR accessory and a Zn-Se crystal that allows collection of FTIR spectra directly on sample without any special preparation (Alpha-P, Bruker Optics, Milan, Italy). The “pressure arm” of the instrument was used to apply constant pressure to the samples positioned on the top of the Zn-Se crystal, to ensure a good contact between the sample and the incident IR beam. All FTIR spectra were collected in the range from 4000 to 400 cm^{-1} , at a spectrum resolution of 4 cm^{-1} and with 32 co-added scans. Background scan of the clean Zn-Se crystal was acquired prior to sample scanning.

2.14 Porosity

2.14.1 Total pores

Oil imbibition was exploited for total porosity determination (Khosravi & Azizian, 2016). Samples (2×2 cm square shape) were immersed into oil until constant weight, as described in section 2.14. Based on oil density (0.89 g/cm^3), the oil volume absorbed by samples was calculated and used to estimate total porosity (%). In particular, the latter was calculated as the

ratio between the volume of the absorbed oil and sample specific volume determined as described in section 2.10.

2.14.2 Mesoporous structures

A gas analyzer was employed with nitrogen gas at -196 °C to investigate sample mesoporous structures, i.e. pore diameter, pore volume and specific surface area. The latter were determined based on Brunauer-Emmett-Teller (BET) model (Braunauer, Emmett, & Teller, 1938). Samples were cut using a sharp scissors and sieved to obtain particles in the range 1-2 mm, and dried at 110 °C for 2 h in an oven (UM100, Memmert, Schwabach, Germany). No significant changes in sample weight was detected upon this pre-treatment. Then, about 10 mg of sample, accurately weighted, was placed inside the analyzer. Pore diameter, pore volume and specific surface area of 1 g-sample were obtained after 24 h. The ratio % between mesopore total volume and total pore volume, determined as described in paragraph 2.14.1, was used to determined mesopore total volume ratio. The latter was defined as the contribution of mesopores to sample total pore volume.

2.14.3 Macroporous structures

Pore dimension was estimated based on image analysis of optical microscopic images by using Image-Pro® Plus (ver. 6.3, Media Cybernetics, Inc., Bethesda, MD, USA). Images were divided into 8 sections and the longitudinal radius (μm) of 10 pores present in each section were measured by comparison with a 50 μm scale. Total macropore volume and macropore total volume ratio were estimated by the difference between data relevant to total pores and mesopores.

2.15 Water and oil absorption kinetics

Samples of 2 × 2 cm square shape were introduced into 50 mL beakers previously filled with 15 mL of water or sunflower oil and maintained at room temperature. The complete immersion of samples in the liquid phase was assured by using a plastic filter, preventing sample from floating. At defined time intervals, samples were withdrawn, wiped with absorbing paper and

weighted. Absorbed water or oil was expressed as the ratio between weight gain at time t and the initial weight of the dried sample. The immersion of sample into water or oil was prolonged until a constant weight after three consequent readings was reached.

Absorption kinetic data were then elaborated by fitting a two-phase exponential decay model (eq. 4) (Blake, Co, & Marangoni, 2014).

$$y = y_{fast}(1 - e^{(-k_{fast}t)}) + y_{slow}(1 - e^{(-k_{slow}t)}) \quad (4)$$

$$y_{max} = y_{fast} + y_{slow} \quad (5)$$

where y_{fast} and y_{slow} are the asymptote values of the fast- and slow-decaying components, respectively, k_{fast} and k_{slow} are the rate constants for the fast- and slow-decaying component, respectively, and y_{max} is the maximum amount of absorbed water or oil when time t tends to infinite and is the sum of y_{fast} and y_{slow} (eq. 5). The value y_{max} can also be considered the theoretical *plateau* value.

2.16 Water and oil absorption capacity

Water and oil absorbing capacities of dried leaves were calculated from water and oil absorption data (Section 2.14), as the amount of water or oil (g) present in 1 g of sample at the absorption *plateau* value (y_{max}).

2.17 Data analysis

All determinations were expressed as the mean \pm standard error of at least two repeated measurements from two experiment replicates ($n \geq 4$). Statistical analysis was performed by using R v. 3.0.2 (The R foundation for Statistical Computing). Student's t-test was used to determine statistical significant differences among means ($p < 0.05$). Non-linear regression analysis of absorbed water and oil as a function of sample mass was performed by using TableCurve2D software (Jandel Scientific, ver. 5.01). Levenberg-Marquardt algorithm was used to perform least squares function minimization and the goodness of fit was evaluated based on statistical parameters of fitting (R^2 , p , standard error) and the residual analysis.

3 Results and discussion

3.1 Characterization of salad waste

Salad waste composition was determined, as shown in Table 1, to highlight the presence of ethanol CO₂-soluble compounds, which, along with water, are expected to be lost upon supercritical-CO₂-drying

Beside water, other compounds such as fat, polyphenols and chlorophylls can be easily dissolved during the supercritical-CO₂ treatment (Fiori, de Faveri, Casazza, & Perego, 2009; Guedes et al., 2013; Lan, Wu, Zhang, Hu, & Liu, 2011; Roy, Goto, Kodama, & Hirose, 1996). These compounds represented about 3.87% of salad waste dry weight. This suggests that the change in salad waste properties upon supercritical-CO₂-drying should be attributed not only to water removal but also to the loss of these compounds.

3.2 Characterization of supercritical-CO₂-dried salad waste

Waste external leaves from fresh-cut Iceberg salad processing were submitted to supercritical-CO₂-drying after substituting compositional water with ethanol. Figure 1 shows the effect of this procedure on visual appearance, color and microscopic structure of salad waste.

Dried salad waste completely lost the original green color. Red point significantly increased while yellow point decreased. This can be attributed to tissue bleaching upon pigment extraction from salad leaves during immersion into ethanol. An increase in luminosity (L*) was also observed (Figure 1), probably due to an increase in light scattering phenomena, generally associated to materials with a high surface roughness (Krokida, Maroulis, & Saravacos, 2001).

The micrographs (Figure 1) showed that fresh tissue cells were regular in shape and appeared turgid with well-defined cell wall structure. Stoma leaf cells were also evident. Supercritical-CO₂-drying did not affect cell integrity but promoted cell swelling as well as the increase of intercellular space. It is likely that cell expansion occurred during the decompression phase, which is required to remove pressurized CO₂ from the sample after drying. Swelling phenomena upon supercritical-CO₂-drying has also been reported for other vegetable matrices, such as

carrot (Brown et al., 2008). By contrast, most bioaerogels have been reported to undergo severe shrinkage upon both ethanol substitution and supercritical-CO₂-drying, as a result of the different structural organization of the gel network depending on the solvent nature (Therkelsen, 1993).

To investigate the physico-chemical characteristics of the material obtained by supercritical-CO₂-drying of salad waste, its thermal and mechanical properties were analyzed (Table 2). Specific heat of the sample resulted in the same range of that reported in the literature for other dried vegetable materials (Mykhailik & Lebovka, 2013). Based on stress-strain diagrams (Supplementary Figure A), CO₂-dried salad waste resulted a brittle material, presenting low values of tensile strength and deformation at break. This can be regarded as a positive attribute of the material, since, differently from other food-grade bioaerogels (Manzocco et al., 2017), it is not hard and could be thus directly used in food systems. To better characterize the properties of this material, apparent density was evaluated, resulting in a very low value, corresponding to a high specific volume (Table 2). These properties suggest that a light weighted and porous material was obtained upon supercritical drying. Total sample porosity was thus evaluated exploiting oil imbibition technique (Khosravi & Azizian, 2016). According to the latter, oil absorption into porous materials such as synthetic aerogels leads firstly to the imbibition of smaller-size pores and then to the imbibition of larger ones, until reaching a *plateau*. It is thus likely that the latter value can be used to estimate total pore volume. Total pore volume and porosity of the material obtained by supercritical-CO₂-drying of salad waste is reported in Table 3. To get an insight into the porous structures of the obtained material, BET analysis, which is conventionally applied to analyze mesopore surface, volume and dimension was also exploited (Wiman et al., 2012) (Table 3). Supplementary Figure B reports an example of the nitrogen isotherms obtained by BET analysis. The latter revealed the presence of mesoporous structures presenting an average dimension of 47 nm. As expected, the value of internal surface area resulted much higher than that reported by Amin, Abkenar, & Zendehboudi (2015), for an air-

dried water fern intended for oil spill absorption ($4.7 \text{ m}^2/\text{g}$). This difference is attributable to the capacity of supercritical- CO_2 -drying to hinder structural collapse, due to the absence of surface tension during the drying treatment (Michalska, Wojdyło, Lech, Łysiak, & Figiel, 2017). Moreover, it can also be due to the cellular structure swelling clearly observed in microscopic images (Figure 1). Interestingly, sample internal surface area resulted in the same range of that reported by Ghafar et al. (2017) and Ubeyitogullari & Ciftci (2017) for aerogels obtained via supercritical- CO_2 -drying of hydrogels containing different biopolymers such as guar galactomannan ($99\text{--}333 \text{ m}^2/\text{g}$) and nanoporous starch ($60\text{--}63 \text{ m}^2/\text{g}$). It is noteworthy that mesopores detected by BET analysis presented an average total volume pore of about $2.8 \text{ cm}^3/\text{g}$, contributing to the total sample pore volume by only 11%. Based on these observations, it is likely that most pores in the sample were not accounted for by these mesopores but rather by larger macropores, corresponding to cellular voids left upon removal of water and other compounds that are soluble in ethanol or CO_2 . These cellular voids were not detectable by BET technique but clearly observed in photomicrographs (Figure 1). The latter actually showed these cell voids to present dimensions much higher than those estimated for mesopores by BET technique (Table 3). Based on this hypothesis, 89% of the sample pore volume, corresponding to a value of about $22.8 \text{ cm}^3/\text{g}$, was developed by macropores (Table 3).

It is noteworthy that the obtained values of internal surface area and total porosity, associated to density lower than $0.5 \text{ g}/\text{cm}^3$ (Table 2) are typical of aerogels (Fricke & Tillotson, 1997). Based on these data, the sample obtained by supercritical- CO_2 -drying of salad waste leaves can be regarded as a bioaerogel-like material.

3.3 Interaction of supercritical- CO_2 -dried salad waste with solvents

The large specific surface area of bioaerogels can be exploited for sorption of bioactives and has been proposed for controlled release in pharmaceutical, food applications and innovative active food packaging. The sorption isotherm of the bioaerogel-like material obtained from salad waste was assessed to obtain preliminary information about the possibility of the material

to interact with hydrophilic volatiles (Figure 2). It must be noted that BET model is known to be valid for low a_w values, as well appreciable in Figure 2 (van den Berg, 1985). Regression analysis in the a_w range 0.05-0.43 provided good model fitting to data ($R^2=0.999$; $p<0.05$). The isotherm shape revealed the presence of a type III isotherm. This is typical of materials able to only weakly interact with water, leading to a strong increase in a_w values upon a reduced moisture increase (Figure 2). In particular, the material obtained by supercritical- CO_2 -drying of salad waste is expected to mainly interact with water through capillarity phenomena in its porous structure as well as through surface interactions with the hydrophilic residues present on cellulosic fibers, which are the main constituents of vegetable cell walls (Al-Muhtaseb, McMinn, & Magee, 2002; Brunauer, Deming, Deming, & Teller, 1940). Given the limited capacity to interact with water vapor, the material obtained by submitting salad waste to supercritical- CO_2 -drying would be physically stable under a wide range of humidity values (Figure 2). This property suggests a possible exploitation of this material for different applications, including biodegradable and edible packaging.

To better characterize material interactions with water vapor, its hygroscopicity was evaluated by moisture sorption kinetics (Supplementary Figure C). Moisture sorption evolved rapidly and reached a final value of about 30% within the first 20 h. This can be related to the inherent hygroscopicity of the material, rich in hydrophilic residues (Ahmadi et al., 2016), as confirmed by the FTIR spectra of the material (Supplementary Figure D). In particular, the broad band in the IR region from $3700\text{-}3000\text{ cm}^{-1}$ and the peak at 667 cm^{-1} have been associated to OH-stretching vibrations arising from hydrogen bonding and to OH out-of plane bending, respectively (Abid, Cabrales, & Haigler, 2014).

As reported for bioareogels, the high porosity of supercritical- CO_2 -dried salad waste could be exploited to entrap huge amounts of different solvents (Ahmadi et al., 2016; Manzocco et al., 2017). The capacity of supercritical- CO_2 -dried sample to load water and oil was thus evaluated by immersing dried leaves in the two solvents (Figure 3). Bioareogel salad waste did not lose

integrity upon immersion into both water and oil, taking the appearance shown in Supplementary Figure E.

It is noteworthy that different results were observed for other bioaerogels reported in the literature. For instance, k-carrageenan bioaerogels, although maintaining their structure upon oil immersion, quickly dissolved in water (Manzocco et al., 2017).

Water and oil were progressively absorbed by dried salad waste during immersion in the solvent, reaching a *plateau* value after about 40 h immersion (Figure 3). Liquid absorption by a porous material is known to be affected by different factors, such as the capacity of the material to bind the solvent (Blake, Co, & Marangoni, 2014). To further investigate these aspects, water and oil absorption kinetic of dried salad waste were fitted using a two-phase exponential decay model (TPE) (eq. 4) (Blake et al., 2014). The latter can be used to describe solvent absorption kinetics as a result of fast and slow components, which are related to the capacity of the material to bind the solvent. Data were well adapted to the model, leading to parameter estimates reported in Table 4. The TPE model used in the analysis posits that solvent absorption in the material obtained by supercritical-CO₂-drying takes place according to two different phases: the first one in which solvent is loaded relatively quickly (fast phase) and the second one in which solvent is loaded relatively slowly (slow phase), both of which can be differentiated based on the respective rate constants. The fast component refers to unbound or weakly bound (physically-entrapped) solvent while the slow component is relevant to bound solvent. The rate constant for the fast-decaying and slow-decaying components (k_{fast} and k_{slow}) resulted similar ($p \geq 0.05$) for water. This indicates that water absorption was equally distributed between fast and slow components, suggesting water to be both physically entrapped and chemically bound. By contrast, in the case of oil, k_{fast} resulted much higher than k_{slow} , confirming its uptake in the material to be mainly driven by physical interactions. Absorption data were further elaborated to evidence the amount of water and oil absorbed in the fast and slow phases. Data indicate that both y_{fast} and y_{slow} resulted higher for water than oil, indicating

that the material presented a higher affinity toward water than oil. Moreover, the maximum amount of absorbed water and oil (y_{max}) was estimated. Given the different density of water and oil, y_{max} was expressed as both weight and volume absorbed by 1 g of dried sample. Results indicate that the water amount absorbed by dried salad waste was significantly higher than the oil one ($p < 0.05$).

It can be noted that supercritical- CO_2 -dried salad absorbed an amount of water much higher than that originally entrapped in the fresh salad tissue. The latter presented a water content of 941 g/kg, corresponding to about 16 g of water for 1 g of dry sample. The enhanced ability of the material to absorb water (Table 2) could be attributed to its peculiar structure (Figure 1). However, it could be inferred that removal of compounds soluble in ethanol or CO_2 could lead to the exposure of hydrophilic functional groups on the surface of the fibrous network. These features would favor capillary forces and swelling phenomena, leading to both water physical entrapment and hydration of functional groups of polysaccharides. On the contrary, oil absorption would be mainly driven by capillary forces, being hindered by the hydrophilic nature of pore surfaces (Ahmadi et al., 2016). It is noteworthy that the water and oil absorption capacity showed by dried salad waste (Table 4) are much higher than those of other bioaerogels reported in the literature. In particular, Ahmadi et al. (2016) and Manzocco et al. (2017) obtained whey protein and k-carrageenan bioaerogels characterized by a maximum oil loading capacity of *circa* 0.025 and 0.800 g/g respectively. These findings suggest that dried salad waste can be resembled to a cloth which can uptake large amounts of water or oil. It could be exploited as template for structuring and delivering both hydrophilic and lipophilic compounds, and thus for the preparation of innovative materials to be used as oil spills absorbers or templates for hydrogels and oleogels.

Conclusions

An expanded, brittle and highly porous material was obtained by supercritical- CO_2 -drying of salad waste. This material was demonstrated to absorb considerable amounts of water and oil.

As other organic aerogels, this dried material is made from renewable sources and is completely biodegradable. Moreover, it is based on the exploitation of an industrial discard, which is always available and cheap. Based on these considerations, bioaerogel-like materials derived from supercritical-drying of salad waste could fit typical bioaerogel applications, such as thermal insulation, biodegradable packaging development and carriers for lipophilic compounds. In addition, the low firmness of dried salad waste and its capacity to withstand water contact without losing integrity suggest further possible applications, including the use as food ingredient, moisture absorber and carrier for hydrophilic molecules. Moreover, it must be underlined that the approach here proposed could be easily applied for the valorization of food industry discards other than fruit and vegetable wastes. However, in order to assess the actual feasibility of this valorization strategy for vegetable waste, the evaluation of sustainability, economic and consumer impact of the obtained material should be carefully investigated. In particular, the high costs of supercritical-CO₂-drying technology could represent a critical issue. Similarly, the perishable nature of salad waste, which is prone to microbiological spoilage in few hours, would impose a selection of salad waste to remove bruised and spoiled parts and a subsequent quick transformation into a dried material. Finally, specific approaches should be adopted to provide the bioaerogel-like material with the desired shape, making it independent on the original dimension of the used vegetable waste. To this regard, the application to the ground vegetable waste of approaches commonly used to produce hydrogel and oleogel templates could be evaluated.

This research did not receive any specific grant from funding agencies in the public, commercial, or not-for-profit sectors.

References

- Abid, N., Cabrales, L., & Haigler, C. H. (2014). Changes in the cell wall and cellulose content of developing cotton fibres investigated by FTIR spectroscopy. *Carbohydrate Polymers*, *100*, 9-16.
- Ahmadi, M., Madadlou, A., & Saboury, A. A. (2016). Whey protein aerogel as blended with cellulose crystalline particles or loaded with fish oil. *Food Chemistry*, *196*, 1016-1022.
- Al-Muhtaseb, A. H., McMinn, W. A. M., & Magee, T. R. A. (2002). Moisture Sorption Isotherm Characteristics of Food Products: A Review. *Food and Bioprocess Processing*, *80*, 118-128.
- Amin, J. S., Abkenar, M. V., & Zendehboudi, S. (2015). Natural sorbent for oil spill cleanup from water surface: Environmental implication. *Industrial & Engineering Chemical research*, *54*, 10615-10621.
- AOAC (1997). Official methods of analysis. Washington, DC: Association of Official Analytical Chemists.
- Blake, A. I., Co, E. D., & Marangoni, A. G. (2014). Structure and physical properties of plant wax crystal networks and their relationship to oil binding capacity. *Journal of the American Oil Chemists' Society*, *91*, 885-903.
- Braunauer, S., Emmett, P. H., & Teller, E. (1938). Adsorption of gases in multimolecular layers. *Journal of the American Chemical Society*, *60*, 309-319.
- Brown, Z. K., Fryer, P. J., Norton, I. T., Bakalis, S., & Bridson, R. H. (2008). Drying of foods using supercritical carbon dioxide - Investigations with carrot. *Innovative Food Science & Emerging Technologies*, *9*, 280-289.
- Brunauer, S., Deming, L. S., Deming, W. E., & Teller, E. (1940). On a Theory of the van der Waals Adsorption of Gases. *Journal of the American Chemical Society*, *62*, 1723-1732.
- Chen, Z., Zhu, C., Zhang, Y., Niu, D., & Du, J. (2010). Postharvest biology and technology effects of aqueous chlorine dioxide treatment on enzymatic browning and shelf-life of

463 fresh-cut asparagus lettuce (*Lactuca sativa* L.). *Postharvest Biology and Technology*, 58,
 464 232-238.

465 Comin, L. M., Temelli, F., & Saldaña, M. D. A. (2012). Barley β -glucan aerogels as a carrier
 466 for flax oil via supercritical CO₂. *Journal of Food Engineering*, 111(4), 625-631.

467 Fiori, L., de Faveri, D., Casazza, A. A., & Perego, P. (2009). Grape by-products: extraction of
 468 polyphenolic compounds using supercritical CO₂ and liquid organic solvent-a preliminary
 469 investigation. *CyTA-Journal of Food*, 7, 163-171.

470 Fricke, J., & Tillotson, T. (1997). Aerogels: production, characterization, and applications. *Thin*
 471 *Solid Films*, 297, 212-223.

472 García-González, C. A., Camino-Rey, M. C., Alnaief, M., Zetzl, C., & Smirnova, I. (2012).
 473 Supercritical drying of aerogels using CO₂: Effect of extraction time on the end material
 474 textural properties. *The Journal of Supercritical Fluids*, 66, 297-306.

475 Ghafar, A., Gurikov, P., Subrahmanyam, R., Parikka, K., Tenkanen, M., Smirnova, I., &
 476 Mikkonen, K. S. (2017). Mesoporous guar galactomannan based biocomposite aerogels
 477 through enzymatic crosslinking. *Composites Part A*, 94, 93-103.

478 Guedes, A. C., Gião, M. S., Matias, A. A., Nunes, A. V. M., Pintado, M. E., Duarte, C. M. M.,
 479 & Malcata, F. X. (2013). Supercritical fluid extraction of carotenoids and chlorophylls a,
 480 b and c, from a wild strain of *Scenedesmus obliquus* for use in food processing. *Journal*
 481 *of Food Engineering*, 116, 478-482.

482 Ivanovic, J., Milovanovic, S., & Zizovic, I. (2016). Utilization of supercritical CO₂ as a
 483 processing aid in setting functionality of starch-based materials. *Starch - Stärke*, 68, 821-
 484 833.

485 Khosravi, M., & Azizian, S. (2016). A new kinetic model for absorption of oil spill by porous
 486 materials. *Microporous and Mesoporous Materials*, 230, 25-29.

487 Krokida, M. K., Maroulis, Z. B., & Saravacos, G. D. (2001). The effect of the method of drying
 488 on the colour of dehydrated products. *International Journal of Food Science and*

489 *Technology*, 36, 53-59.

490 Lan, S., Wu, L., Zhang, D., Hu, C., & Liu, Y. (2011). Ethanol outperforms multiple solvents in
 491 the extraction of chlorophyll-a from biological soil crusts. *Soil Biology and Biochemistry*,
 492 43, 857–861.

493 Lichtenthaler, H. K., & Buschmann, C. (2001). Chlorophylls and carotenoids: Measurement
 494 and characterization by UV-VIS spectroscopy. *Current Protocols in Food Analytical*
 495 *Chemistry*, F4:3.1-F4:3.8.

496 Maleki, H. (2016). Recent advances in aerogels for environmental remediation applications: A
 497 review. *Chemical Engineering Journal*, 300, 98-118.

498 Manzocco, L., Valoppi, F., Calligaris, S., Andreatta, F., Spilimbergo, S., & Cristina, M. (2017).
 499 Exploitation of k -carrageenan aerogels as template for edible oleogel preparation. *Food*
 500 *Hydrocolloids*, 71, 68-75.

501 Michalska, A., Wojdyło, A., Lech, K., Łysiak, G. P., & Figiel, A. (2017). Effect of different
 502 drying techniques on physical properties, total polyphenols and antioxidant capacity of
 503 blackcurrant pomace powders. *LWT - Food Science and Technology*, 78, 114-121.

504 Mykhailiyk, V., & Lebovka, N. I. (2013). Specific heat of apple at different moisture contents
 505 and temperatures. *Journal of Food Engineering*, 123, 32-35.

506 Plazzotta, S., Manzocco, L., & Nicoli, M. C. (2017). Fruit and vegetable waste management and
 507 the challenge of fresh-cut salad. *Trends in Food Science & Technology*, 63, 51-59.

508 Perucka, I., Olszówka, K. & Chilczuk, B. (2014). Changes in the chlorophyll content in stored
 509 lettuce *Lactuca sativa* L. after pre-harvest foliar application of CaCl₂. *Acta Agrobotanica*,
 510 66, 137-142.

511 Raak, N., Symmank, C., Zahn, S., Aschemann-Witzel, J., & Rohm, H. (2017). Processing- and
 512 product-related causes for food waste and implications for the food supply chain. *Waste*
 513 *Management*, 61, 461-472.

514 Roy, B. C., Goto, M., Kodama, A., & Hirose, T. (1996). Supercritical CO₂ extraction of

essential oils and cuticular waxes from peppermint leaves. *Journal of Chemical Technology & Biotechnology*, 67, 21–26.

Singleton, V. L., & Rossi, J. A. J. (1985). Colorimetry of total phenolics with phosphomolybdic-phosphotungstic acid reagents. *American Journal of Enology and Viticulture*, 16, 144–158.

Stergar, J., & Maver, U. (2016). Review of aerogel-based materials in biomedical applications. *Journal of Sol-Gel Science and Technology*, 77, 738-752.

Su, J. F., Huang, Z., Zhao, Y. H., Yuan, X. Y., Wang, X. Y., & Li, M. (2010). Moisture sorption and water vapor permeability of soy protein isolate/poly (vinylalcohol)/glycerol blend films. *Industrial Crops and Products*, 31, 266-276.

Therkelsen, G. H. (1993). Carrageenan. In R. L. Whistler, & J. N. BeMiller (Eds.), *Industrial Gums: Polysaccharides and their derivatives* (Third ed., pp. 146-176). San Diego (USA): Academic Press, Inc.

Ubeyitogullari, A., & Ciftci, O. N. (2017). Generating phytosterol nanoparticles in nanoporous bioaerogels via supercritical carbon dioxide impregnation: Effect of impregnation conditions. *Journal of Food Engineering*, 207, 99-107.

van den Berg, C. (1985). “Development of B.E.T.-like models for sorption of water on foods, theory and relevance”. In *Properties of water in foods: in relation to quality and stability*, edited by D. Simatos and J L Multon, 119-131. Nato ASI Series: Springer.

Viganó, J., Machado, A. P. da F., & Martínez, J. (2015). Sub- and supercritical fluid technology applied to food waste processing. *The Journal of Supercritical Fluids*, 96, 272-286.

Wiman, M., Dienes, D., Hansen, M. A. T. van der Meulen, T., Lidén, G., & Zacchi, G. (2012). Cellulose accessibility determines the rate of enzymatic hydrolysis of steam-pretreated spruce. *Bioresource Technology*, 126, 208-215.

541 **Figure Captions**

542 Figure 1. Visual appearance, color and microscopic images of fresh salad leaves and salad
543 leaves dried using supercritical CO₂.

544 Figure 2. Isotherm of supercritical-CO₂-dried salad waste. Fitting curve of BET model (BET)
545 to experimental data (Data) is also reported. ds =dry sample.

546 Figure 3. Absorption of water and oil by supercritical-CO₂-dried salad waste. Fitting curves of
547 the two-phase exponential model (TPE) are also reported. ds =dry sample.

548

549 **Supplementary Figure Captions**

550 Supplementary Figure A. Stress-strain diagram of supercritical-CO₂-dried salad waste.

551 Supplementary Figure B. Nitrogen adsorption (ads) and desorption (des) isotherms of
552 supercritical-CO₂-dried salad waste.

553 Supplementary Figure C. Moisture sorption (MS) versus time diagram of the supercritical-
554 CO₂-dried salad waste.

555 Supplementary Figure D. FTIR spectra of supercritical-CO₂-dried salad waste. AU =
556 absorbance unit

557 Supplementary Figure E. Visual appearance of supercritical-CO₂-dried salad waste after
558 immersion in water.

Table 1. Composition of salad waste.

	Amount in fresh salad (g/kg)
Humidity	945 ± 6
Carbohydrates	28.8 ± 0.6
Total dietary fibre	13.3 ± 0.2
Proteins	10.5 ± 0.8
Ash	2.55 ± 0.11
Fat	2.05 ± 0.07
Total polyphenols (GAE)	0.0722 ± 0.0055
Chlorophylls	0.00765 ± 0.00013

Table 2. Specific heat capacity, mechanical properties (tensile strength and elongation at break), apparent density and specific volume of supercritical-CO₂-dried salad waste.

Specific heat capacity (Jg ⁻¹ K ⁻¹)	Tensile strength at break (N)	Elongation at break (mm)	Apparent density (g/cm ³)	Specific volume (cm ³ /g)
2.617 ± 0.034	0.18 ± 0.10	0.21 ± 0.05	0.032 ± 0.004	31.3 ± 3.4

Table 3. Characteristics of mesopores, macropores, and total porosity of supercritical-CO₂-dried salad leaves.

Mesopores ^a				Macropores			Total pores ^d	
Surface area	Total pore volume	Pore dimension	Total pore volume ratio	Total pore volume ^c	Pore dimension ^b	Total pore volume ratio ^c	Total pore volume	Total porosity
(m ² /g)	(cm ³ /g)	(nm)	(%)	(cm ³ /g)	(μm)	(%)	(cm ³ /g)	(%)
112.8 ± 8.2	2.80 ± 0.30	46.8 ± 1.9	10.9 ± 0.2	22.8 ± 0.4	111.1 ± 35.3	89.1 ± 1.6	25.6 ± 0.4	81.7 ± 1.4

^a estimated by BET technique

^b estimated by image analysis of photomicrographs

^c estimated by difference between data of total pores and mesopores

^d estimated by oil imbibition

Table 4. Experimental regression coefficients estimate, R² and adjusted R² for the two-phase exponential model (TPE) and for the solvent spill absorption model (SSA) of water and oil absorption in supercritical-CO₂-dried salad waste. Water and oil absorption capacity is also reported.

	Water	Oil
k_{fast} (h ⁻¹)	0.431 ± 0.013	248.2 ± 13.6
k_{slow} (h ⁻¹)	0.465 ± 0.016	0.175 ± 0.007
y_{fast} (g solvent/g ds)	16.8 ± 0.8	10.6 ± 0.2
y_{slow} (g solvent/g ds)	16.8 ± 0.9	8.5 ± 0.4
y_{max} (g solvent/g ds)	33.5 ± 1.4	19.1 ± 1.3
y_{max} (mL solvent/g ds)	37.6 ± 1.6	21.4 ± 1.5
R ²	0.944	0.967
R ² adj	0.929	0.954
Absorption capacity (g/g)	0.97 ± 0.02	0.95 ± 0.02





Sample	Visual appearance	Color			Optical microscopy
		L*	a*	b*	
Fresh		71.4 ± 1.3	-16.9 ± 1.2	31.6 ± 1.4	
Dried		85.0 ± 2.4	-0.2 ± 0.1	8.7 ± 0.4	

Figure 1. Visual appearance, color and microscopic images of fresh salad leaves and salad leaves dried using supercritical CO₂.

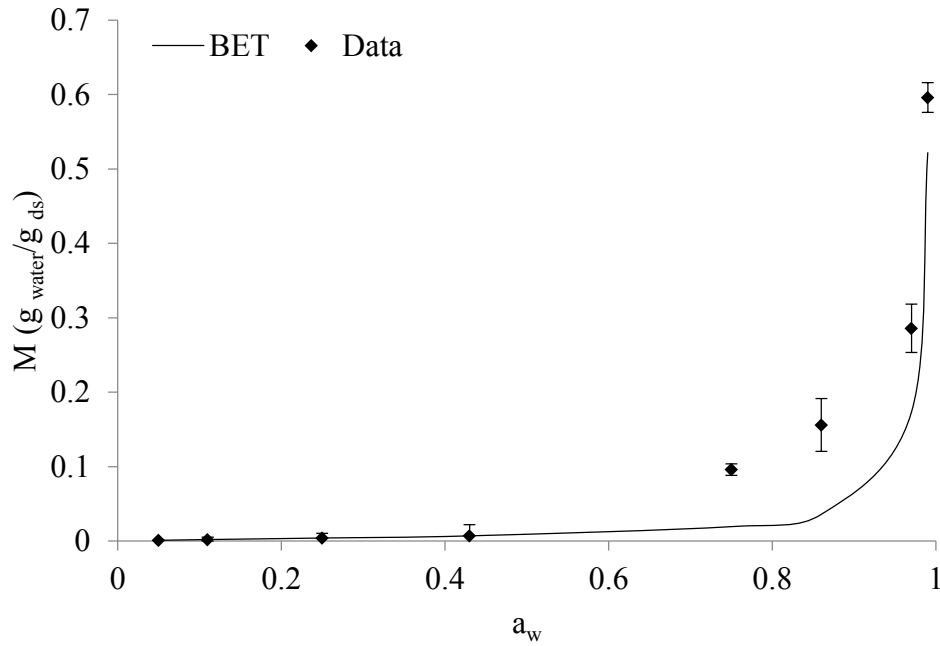


Figure 2. Isotherm of supercritical-CO₂-dried salad waste. Fitting curve of BET model (BET) to experimental data (Data) is also reported. ds =dry sample.



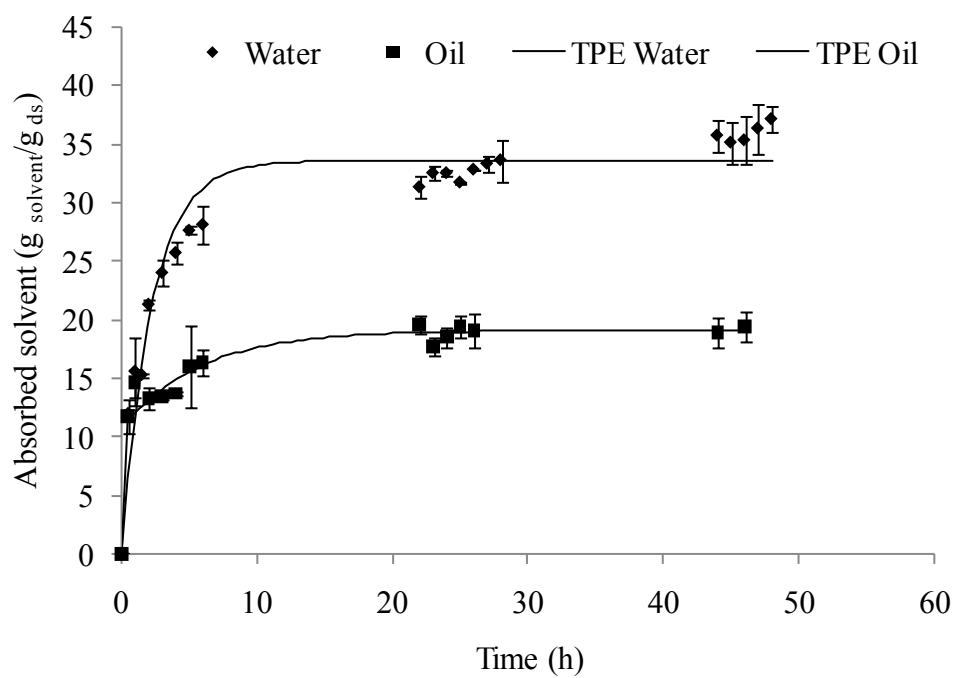


Figure 3. Absorption of water and oil by supercritical-CO₂-dried salad waste. Fitting curves of the two-phase exponential model (TPE) are also reported. ds =dry sample.

1 **Supplementary data**

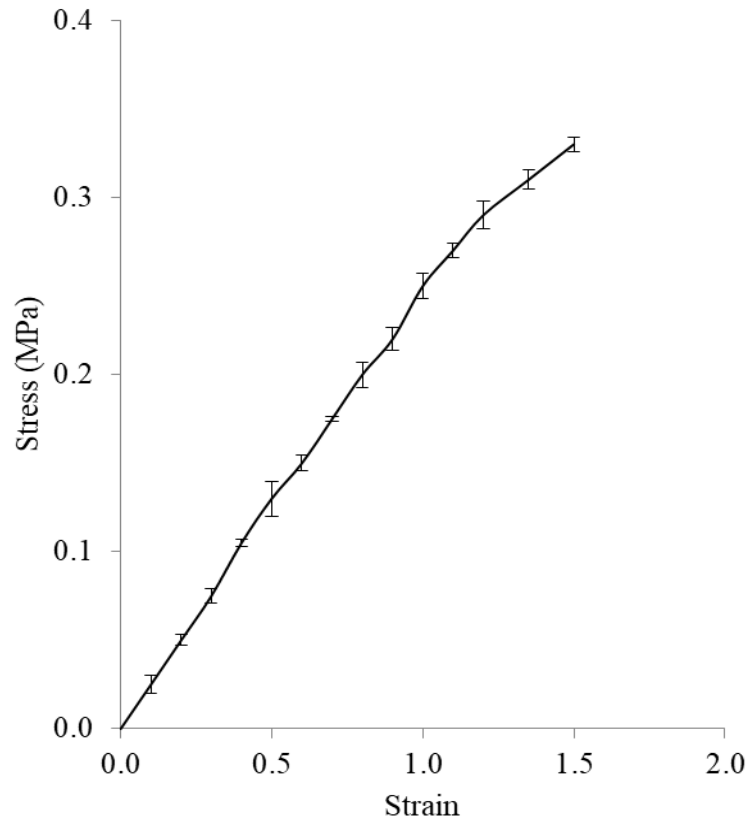


2
3 **Supplementary Figure A. Stress-strain diagram of supercritical-CO₂-dried salad waste.**

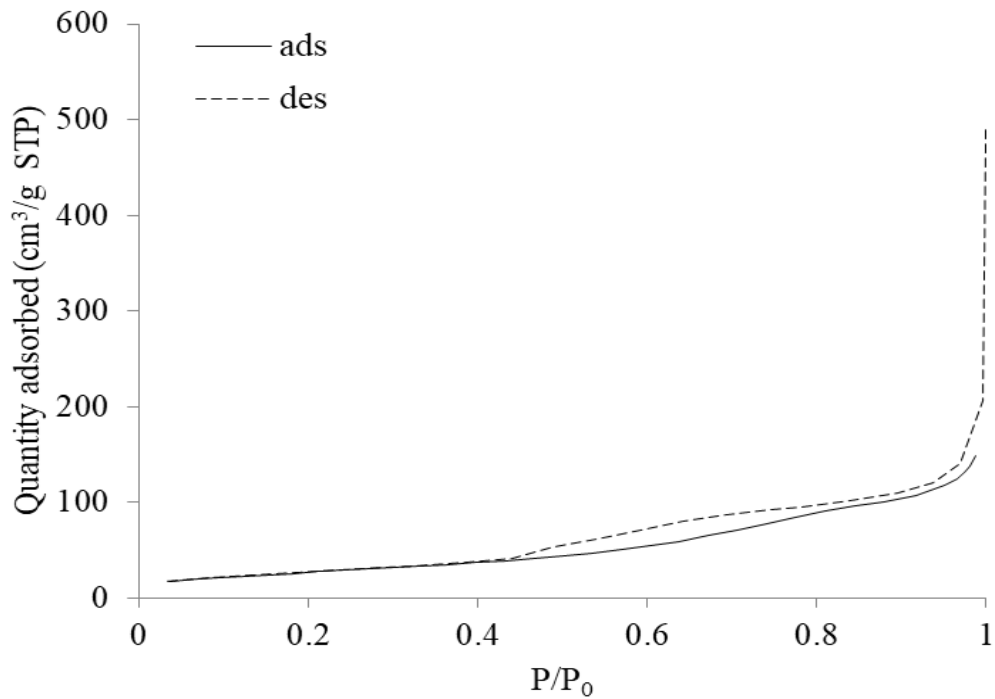

6
7 **Supplementary Figure B. Nitrogen adsorption (ads) and desorption (des) isotherms of**
8 **supercritical-CO₂-dried salad waste.**

11

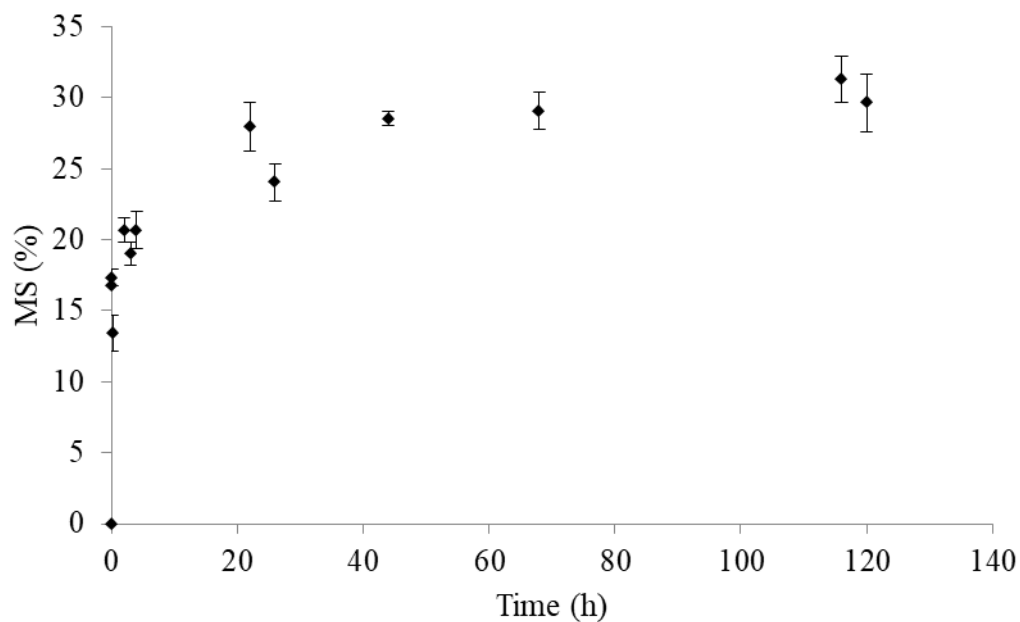

12

13


14

15

16

17

Supplementary Figure C. Moisture sorption (MS) versus time diagram of the supercritical-CO₂-dried salad waste.

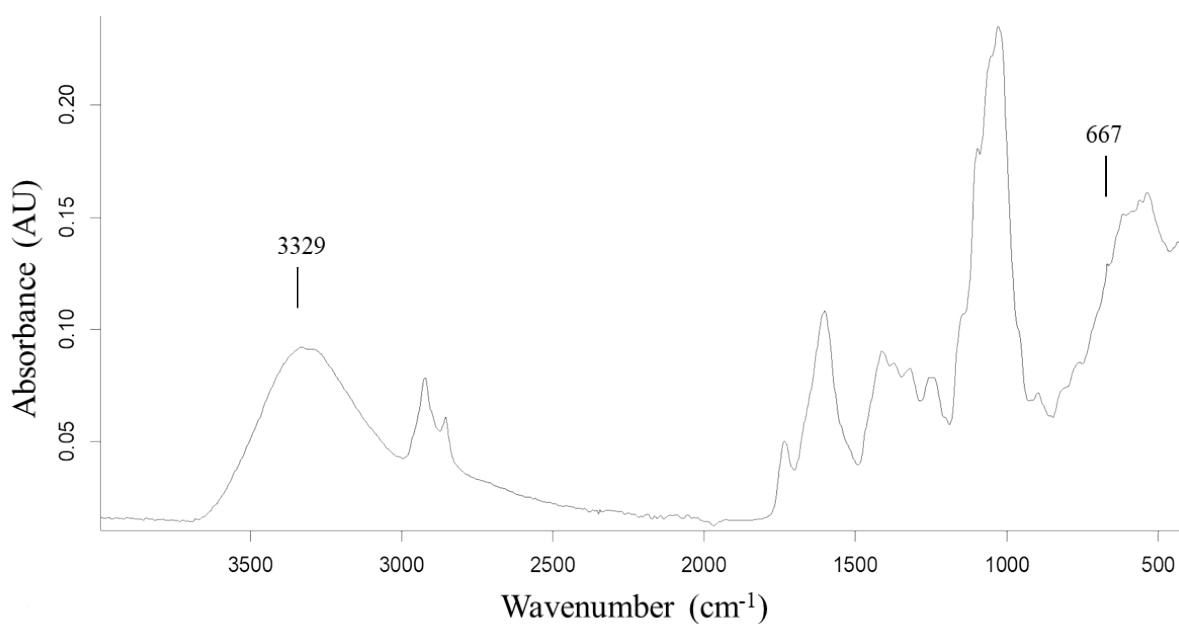

18

19

20

21

Supplementary Figure D. FTIR spectra of supercritical-CO₂-dried salad waste. AU = absorbance unit



22
23 Supplementary Figure E. Visual appearance of supercritical-CO₂-dried salad waste after
24 immersion in water.